
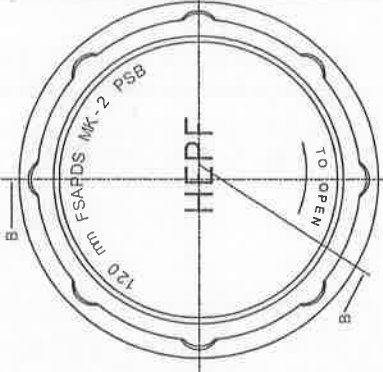


DRG. No	REV
H OMA 120 2 145	1

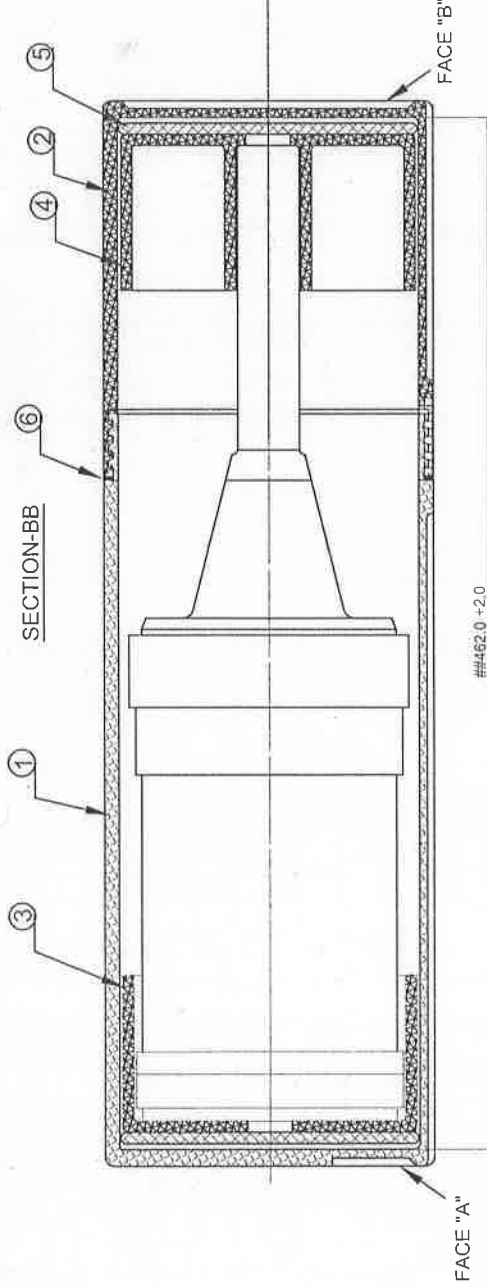

IMPORTANT NOTE: MANUFACTURER SHALL ENSURE ## THIS MARKED DIMENSIONS AND TO BE MEASURED

ALL OTHER DIMENSIONS TO BE ENSURE THE FITMENT/STRENGTH/SAFETY/MANUFACTURING PURPOSE ONLY

1. MATERIAL (FOR ITEM 1, 2, 3 & 4)

HIGH DENSITY POLYETHYLENE TO SPEC.. JSS 9330-03:2014 ORANGE COLOUR.

2. HARDNESS (FOR ITEM NO. 5): CLASS 'C2' 51 TO 55 NOT TO EXCEED HIGH LIMIT

3. ITEM NO. 6 TO BE FREE FROM FLASH ON SURFACE, PRESERVED IN TALC DUST.
TO BE APPLIED WITH SILICON GREASE BEFORE ASSEMBLY.

4. CONTAINER WITH SHOT SHALL CONFORM TO SPEC.. FOR DROP TEST-JSG 0102.

5. ITEM NO. 5 TO BE PASTED INSIDE BOTTOM OF THE ITEM NOS. 1 & 2 RESPECTIVELY

6. DRAFT ANGLE 0.25° UNLESS OTHERWISE SPECIFIED FOR MOULDING PURPOSE

7. ALL SHARP EDGES TO BE ROUNDED OFF WITH R1

8. MARKING :-

"HEPF" AS SHOWN IN ITEM NO. 2 (LID) (TO BE EMBOSSED IN 20 SIZE & 2 THICK AT FACE 'A')

FOLLOWING DETAILS ARE TO BE EMBOSSED IN FACE 'B' OF ITEM NO. 1 (BODY)

⊕ YEAR OF MANUFACTURING
+ 120mm FSAPDS MK-II PSB
= MANUFACTURE'S INITIAL

TO BE EMBOSSED IN
SIZE 8mm X 1.2mm THICKNESS

9. THE PLASTIC CONTAINER SHOULD BE DESIGNED SUCH THAT, FINAL SHOT ASSEMBLY PACKED
ALONG WITH TOP & BOTTOM SLEEVES USING 0.5mm THICK POLYURETHANE BAG SHOULD
FREELY ENTER THE BODY & LID WHILE PACKING.

10. ALL RADIUS DIMS. ARE ONLY FOR REFERENCE (MANUFACTURING PURPOSE ONLY)

SL.NO	DESCRIPTION	MATERIAL	QTY
6	GASKET	NEOPRENE RUBBER TO SPEC: IND/ME/884(PIRV)	1
5	CUSHION PAD	SPONGE RUBBER TO commercial grade	2
4	SLEEVE TOP	NOTE - 1	1
3	SLEEVE BOTTOM	NOTE - 1	1
2	LID	NOTE - 1	1
1	BODY	NOTE - 1	1

ALL DIMENSIONS ARE IN mm

MATERIAL	ALTERATIONS	DATE	LATEST REFERENCE :-
---	Cushion pad material spec IND/ME/645 has amended as commercial grade	07.06.24	DRAWN
HEAT TREAT/GROUND	Lid/body height's amended; Thread profile & dimension amended; In place of triple start thread was amended as single start thread		CHECKD. USER SEC.
---	Dimensions and Tolerances are amended which facilitating to moulding process		CHECKD. QAP
SURFACE TREAT	Dims & Tol amended for moulding & OFB emblem removed		
---	Note 9 added		
SUR. FINISH/COAT			APPROD.
---			DATE
EST MASS PRO/FINAL			SCALE
			NTS
			REV
			DRG. NO:
			H OMA 120 2 145 1

CONTAINER FOR 120mm FSAPDS

MK-II PSB

HIGH ENERGY PROJECTILE FACTORY

TIRUCHIRAPALLI

DRG: No	REV
H OMA 120 2 145	1


① BODY

8 RIBS EQUISPACED



① BODY

4 UPRIGHT SYMBOLS ON CIRCUMFERENCE, BETWEEN ALTERNATIVE RIBS AS SHOWN

SECTION AT BB

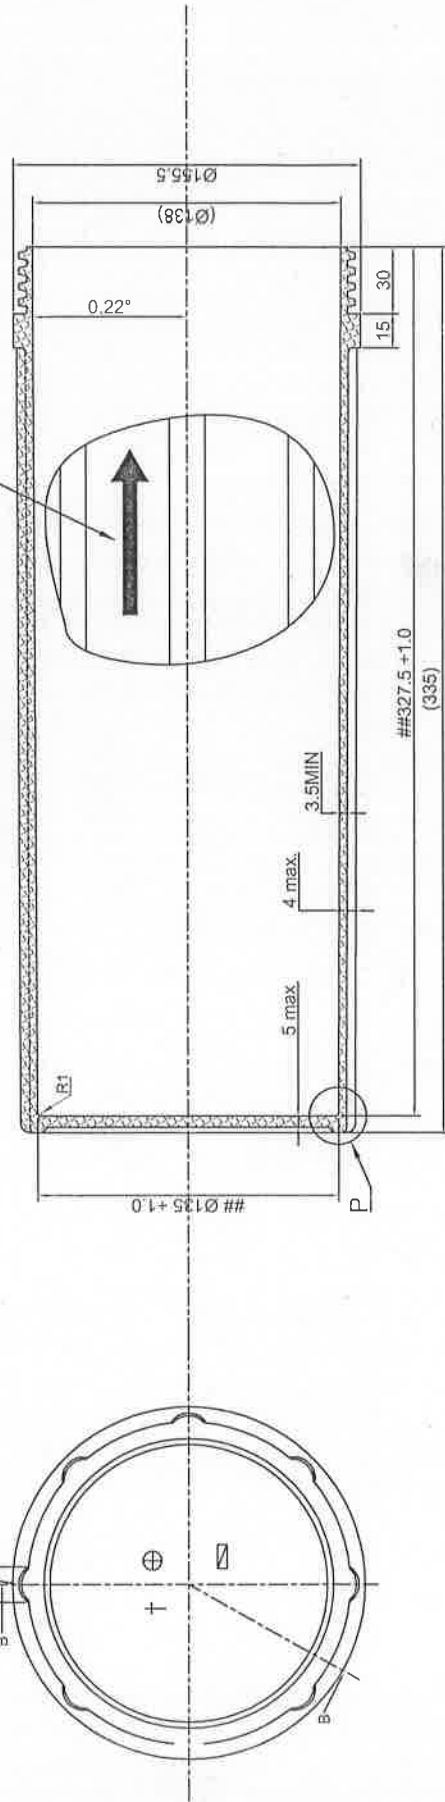



③ SLEEVE BOTTOM

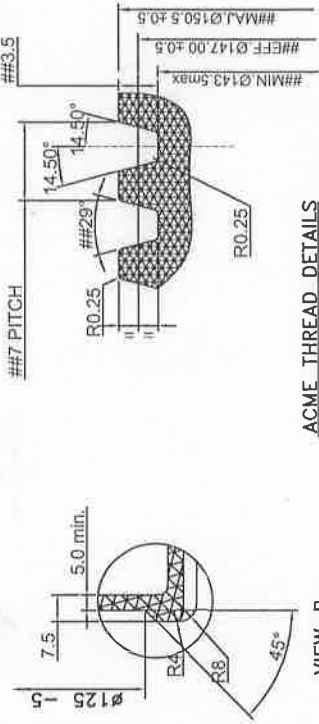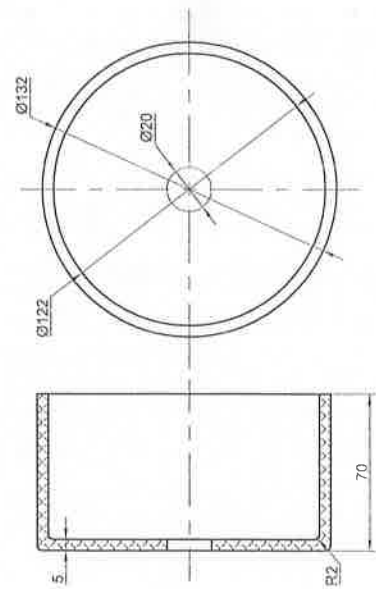


ACME THREAD DETAILS

ALL DIMENSIONS ARE IN mm
REMOVE ALL SHARP EDGES


LATEST REFERENCE :-		DATE	
DRAWN	07.06.24	APPROD.	SHEET
CHECKD. <i>[Signature]</i>		DATE	05.01.05
USER SEC. <i>[Signature]</i>		SCALE	2 OF 3
CHECKD. <i>[Signature]</i>		NTS	
QAP		DRG. NO.	H OMA 120 2 145 1
Cushion pad material spec INO/ME/645 has amended as commercial grade		CONTAINER FOR 120mm FSAPDS	
Lid & body height's amended; Thread profile & dimension amended; In place of triple start thread was amended as single start thread		MK-II PSB	
Dimensions and Tolerances are amended which facilitating to moulding process		HIGH ENERGY PROJECTILE FACTORY	
Dms & Tol amended for moulding & OFB emblem removed.		TIRUCHIRAPALLI	
Note 9 added.			
SURFACE TREAT			
SUR. FINISH/COAT			
EST. MASS PRO/FINAL			

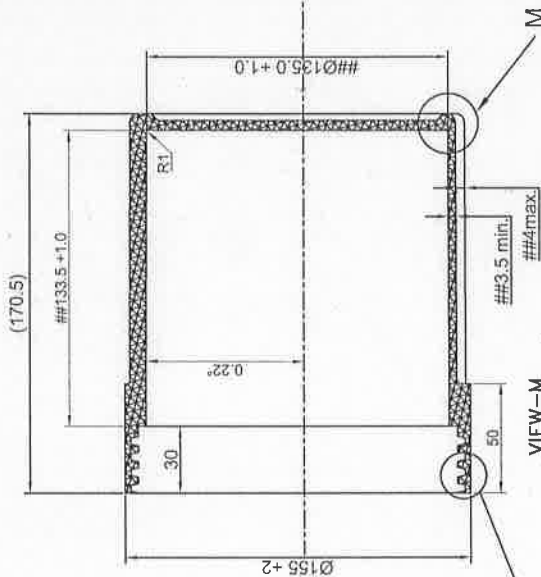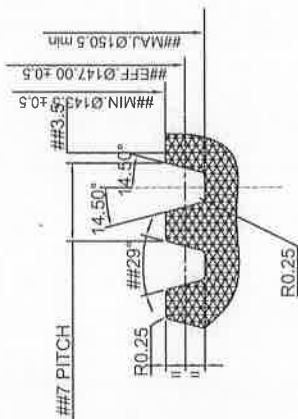② LID

ACME THREAD DETAILS

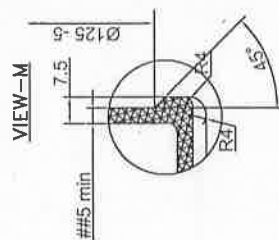


④ SLEEVE TOP

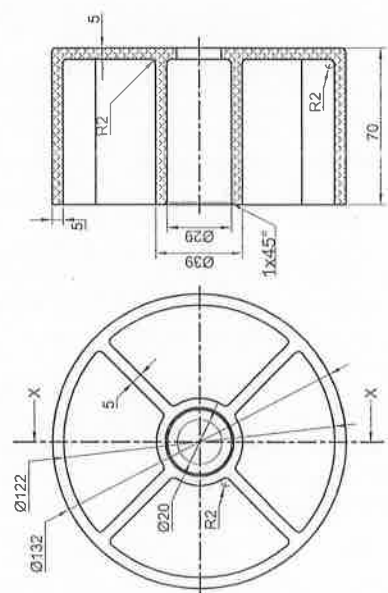


SECTION AT XX

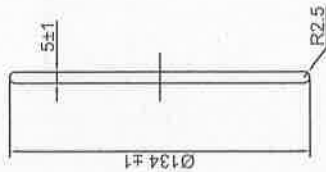




⑤ CUSHION PADS



⑥ GASKET



ALL DIMENSIONS ARE IN mm
REMOVE ALL SHARP EDGES

MATERIAL		Curtain pad material spec IND/ME/645 was amended as commercial grade	LATEST REFERENCE :-
HEAT TREAT/GROUND	1	<p>1. Lid & body heights amended: Thread profile & dimension amended; In place of triple start thread was amended as single start thread</p> <p>2. Dimensions and Tolerances are amended which facilitating to moulding process</p> <p>3. Dims & Tol amended for moulding & OFB emblem removed. Note 9 added.</p>	<p>DRAWN </p> <p>CHECKD. USER </p> <p>CHECKD. </p> <p>QAP </p>
SURFACE TREAT	Rev.	ALTERATIONS	DATE
SUR. FINISH/COAT	TITLE :		APPRD. 
	CONTAINER FOR 120mm FSAPDS MK-II PSB		DATE 05 01 05 3 OF 3
	HIGH ENERGY PROJECTILE FACTORY		SCALE NTS
EST.MASS PRO/FINAL	TIRUCHIRAPALLI		REV
			DRG. NO:
			H OMA 120 2 145 1

MONITORING INSTRUCTION FOR INSPECTION		Issue No. 01 Rev. No. 01
		Date of Issue 10.06.2024
PLASTIC CONTAINER FOR PROOF SHOT REP.120mm MK-II FSAPDS		HAPP/QA/SC/P/003
Rev no	Amendment	Date
1	Item 5 raw mat. amended ; On receipt inspection amended; drg.rev.amended	10.06.24

DRAWING NO. : HAPP Drg. H OMA 120 2 145 REV 1

RAW MATERIAL : 1. For Sl.No. 1,2,3 & 4 - High Density Polyethylene to Spec JSS 9330-03 : 2014 (Type 2) in Orange colour .
2. For Sl. No.6 (Gasket) – Neoprene Rubber To spec IND/ME/884 (Prov.).
3. For sl. No 5 (Cushion Pads) - Sponge Rubber to Commercial Grade
4.End use for Proof Shot Representing 120mm FSAPDS MK-II.

TABLE A. INSPECTION CHECKS TO BE CARRIED OUT ON RAW MATERIAL AT FIRM'S PREMISES

SL. NO.	CHARACTERISTICS	SPECIFICATION / REQUIREMENT	SAMPLE SIZE
1	TESTING	1. JSS 9330-03:2014 CLAUSE 7.4 Test requirements for high density polyethylene: (a) Chemical Requirements (b) Physical Requirements 2. Neoprene rubber to spec: IND/ME/884 (PROV). 3. Sponge Rubber To Spec: Commercial Grade	Two samples/ Lot or batch

NOTES:

- Firm to select raw material samples / test specimens for each heat lot/batch and forwarded to nearby NABL accredited / Govt. Approved for testing and forward test report.
- Based on satisfactory test results, HEPF will accord material clearance to make
 - 10 pilot samples of plastic container for new source suppliers.
 - Bulk supply for existing suppliers.

TABLE B. PILOT SAMPLE INSPECTION TO BE CARRIED OUT ON RECEIPT AT HEPF (NEW SOURCE)

SL. NO.	CHARACTERISTICS	SPECIFICATION / REQUIREMENT	SAMPLE SIZE
1	WORKMANSHIP (VISUAL)	The parts shall be free from damages, bubbles, surface imperfections, porosity, voids due to dust inclusions & other obvious defects likely to impair their usefulness or life	100%
2	DIMENSIONS	As per drawing	100%
3	DROP TEST	As per specification JSG 0102 ??	4 Nos
4	PACKING	Packing slip indicating source code, material grade , lot no. and qty.	100%

- Based on satisfactory test results, HEPF will accord material clearance for bulk production of plastic containers

TABLE C. BULK INSPECTION TO BE CARRIED OUT ON RECEIPT AT HEPF.

SL. NO.	CHARACTERISTICS	SPECIFICATION / REQUIREMENT	SAMPLE SIZE
1	WORKMANSHIP (VISUAL)	The parts shall be free from damages, bubbles, surface imperfections, porosity, voids due to dust inclusions & other obvious defects likely to impair their usefulness or life	100%
2	DIMENSIONS	As per drawing	100%
3	DROP TEST	As per specification JSG 0102	**Random sample 1% per Lot or Batch
4	PACKING	Packing slip indicating source code, material grade , lot no. and qty.	100%


** For lot or batch qty.500 Nos.and above 1% to be subjected drop test, if less than 500 Nos.5 Nos.to be subjected to drop test.


MONITORING INSTRUCTION FOR INSPECTION		Issue No. 01 Rev. No. 01
		Date of Issue 10.06.2024
PLASTIC CONTAINER FOR PROOF SHOT REP.120mm MK-II FSAPDS		HAPP/QA/SC/P/003
Rev no	Amendment	Date
1	Item 5 raw mat. amended ; On receipt inspection amended; drg.rev.amended	10.06.24


TABLE D. FOLLOWING INSPECTION DOCUMENTS MUST BE ENCLOSED ALONG WITH EACH SUPPLY OF FINISHED PRODUCT.


SL. NO.	INSPECTION DOCUMENTS
1	Dimensional inspection report from supplier.
2	Test reports from NABL accredited / Govt. approved for tests mentioned Table no. A.
3	Test reports from NABL accredited / Govt. approved for tests mentioned Table no. B for new sources.
4	Packing slip details
5	Guarantee / warranty certificate
6	In addition to the above, soft copies of all the certificates mentioned shall be sent to following e-mail id's. happqa@ord.gov.in , mmhapp@ord.gov.in

- I. Explicit deviation(s) if any such as typographical error, values, numeric, other parameter, etc is/are found in monitoring instruction of the above stores, the relevant standards conforming to the concerned specifications shall be referred to confirm the parameter.
- II. In case of any damages during inspection at HEPF Trichy, 100% replacement to be done by the firm.
- III. Correspondence w.r.t the quality of supplied material and their acceptance or otherwise is to be made at e-mail id happqa@ord.gov.in


GANDI VIVEK KUMAR RAJA
WM / Q and R&D
MEMBER / TECHNICAL COMMITTEE


R.V. DWARAKANATHAN
DO / ASSY & STP
MEMBER / TECHNICAL COMMITTEE


SREENIVASA RAO BODALA
Jt.GM / E & Q
TECHNICAL EXPERT & CHAIRMAN
TECHNICAL COMMITTEE


SUMANT KUMAR
WM / P
MEMBER / TECHNICAL COMMITTEE

[SPEC II]

Phone : 331449
Telex : 145-264 ARDE IN
Grams : ARMAMENTS

Govt. of India
Ministry of Defence
Armament Res & Dev Estt.
Armament Post, Pashan
Pune - 6 MARCH 96

ARDE/1/3/V/76-TECH

Dated 06-03-96

The General Manager
HAPP,
Trichy - 620 025


Kind Attn - Shri B.P. Mohapatra, DGM


Forwarding Copy of JSG 0102

Ref:- Your telex no HAPP/QA/LP/943364 dated 20-02-96

A copy of JSG 0102 pertaining for drop test of plastic container is forwarded herewith as desired.

Encl: A/A


(KJ SOMAYAJULU)
SC 'F'
JT DIR
FOR DIRECTOR ARDE

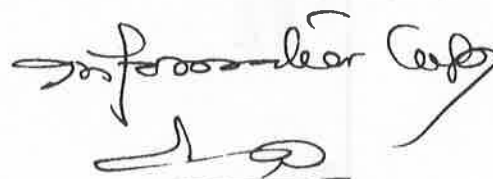
Jm/ee
9/1/96

RESTRICTED

- 37 -

JSG-0102 Part II
May 1984

(a)	(b)	(c)	(d)	(e)
-----	-----	-----	-----	-----

abandoned and a fresh spore suspension prepared for a repeat test.

4. At the end of 28 days, the store shall be removed from the chamber and carefully examined for evidence of mould growth.

- | 14. | 14P
Impact
(vertical) | All Packages | 1. The package shall be allowed to fall freely through a distance 'd' measured between the lowest point of the package and an impacting steel surface of atleast 6 mm thick wet floated steel plate and bolted down to concrete of 0.45 m minimum thickness. | 1. These tests are intended to apply the kind of stresses which arise from drops which could occur in normal handling. Packages weighing upto 70 kg are likely to be manually handled on and off transport vehicles. The 1.5 m drop is chosen as a representative tail board height for current GS trucks. |
|-----|-----------------------------|--------------|--|--|
|-----|-----------------------------|--------------|--|--|

RESTRICTED

...38/-

RESTRICTED

- 38 -

(a)	(b)	(c)	(d)	(e)

2. Heavier stores are subjected to smaller drop heights since services experience shows that the higher drops are more probable for the smaller manually handable stores. Also it would be uneconomical to manufacture heavy packages capable of the higher drops with full serviceability.

Table 1

Package mass	First drop height	Remaining drop heights and number & drops
0-70 kg	one drop of 1.5 m	Six drops of 0.3 m
71-125 kg	one drop of 0.9 m	Six drops of 0.15 m
126-500 kg	one drop of 0.6 m	Six drops of 0.15 m
501 kg upwards	Each end lifted 0.3 m intum and allowed to fall freely.	

Notes

- a) Packages upto 250 kg shall be capable of withstanding one major drop in any orientation as in the second column of Table 1, followed by the number of nominally flat minor drops into the designated base or lid of the package as detailed in the third column.

RESTRICTED

.....39/-

RESTRICTED

- 39 -

JSG-0102 Part II

May 1984

(a)	(b)	(c)	(d)	(e)
		b) For rectangular packages, the face, corner or edge selected for the major impact shall normally be that which is the most vulnerable in terms of damage to the contents.		3. The package shall be considered to have failed the test if the container or its contents are unserviceable or if the package is affected in any way which could cause the contents to become unsafe or unserviceable. Failure may not become apparent until the test package has been subjected to other tests carried out in sequence with this test.
		c) Cylindrical packages shall be dropped in any orientation as in the second column of Table 1 followed by the number of nominally flat drops onto the designated base or head as in the third column.		4. The trial requirements should define the package face or faces which are to be subjected to impact. The method of face identification and marking is to be as shown in Appendix 'F'.
		d) Package over 250 kg upto and including 500 kg shall be capable of withstanding the major drop of the second column of table 1; onto the designated base of package.		
		e) Packages of over 500 kg shall be capable of withstanding the free end of drop as in Table 1.		

Information Copy
7/11/90
7/11/90

401



रक्षा मंत्रालय
MINISTRY OF DEFENCE

संयुक्त सेवा स्पेसिफिकेशन
JOINT SERVICES SPECIFICATION

ON

**POLYETHYLENE LOW DENSITY, LINEAR LOW
DENSITY AND HIGH DENSITY**

DS Cat. Nos.

Polyethylene Low Density Type 1	9330 - 000 115
Polyethylene Low Density Type 2	9330 - 000 131
Polyethylene Linear Low Density	9330 - 000 130
Polyethylene High Density Type 1	9330 - 000 117
Polyethylene High Density Type 2	9330 - 000 119

मानकीकरण निदेशालय
रक्षा उत्पादन विभाग
रक्षा मंत्रालय
'एच' ब्लॉक, निर्माण भवन डाकघर
नई दिल्ली - 110 011

DIRECTORATE OF STANDARDISATION
DEPARTMENT OF DEFENCE PRODUCTION
MINISTRY OF DEFENCE
'H' BLOCK, NIRMAN BHAWAN PO
NEW DELHI - 110 011

LIST OF MEMBERS ASSOCIATED WITH FORMULATION OF THIS STANDARD

1. This Joint Services Specification has been approved by Dr. DK Kharat, Sc 'G' Director, Tech (Armaments), DRDO, Chairman, Armament Standardisation Sub - Committee.
2. The following members have been present / consulted in preparing the document :-

Sl. No.	Name & Designation	Organisation
1.	Shri S.K Rastogi, Sc 'F' Additional Director	Dte of Armaments, DRDO Orgn, New Delhi
2.	Col SK Mohan	ADGWE / GS (WE - 2 / 3), New Delhi
3.	Col RN Nambiar	Dte of Arty (GS / Artillery - 5), New Delhi
4.	Shri B.P. Singh, DONA	Dte Gen of Naval Armt, Naval HQ, New Delhi
5.	Air Cmde R Kumar, PDA	Dte of Armt & Safety Eqpt, Air HQ, New Delhi
6.	Lt. Col K.S Hundal, JD, EME, Armt	DGEME, Army HQ, New Delhi
7.	Commander Shrinivas	DGNAI, Naval HQ, New Delhi
8.	Shri A.K. Parashar, PScO	DGAQA, JD (Armt) Gp, New Delhi
9.	Dr. R.K Upadhyay, PScO	CQA (ME), Pune
10.	Col G.K Natu	CQA (Amn), Pune
11.	H Saphui, JAG (SG)	CQA (SA), Ichapur, West Bengal
12.	Col V.K Rana	CQA (W), Jabalpur
13.	Dr.[Mrs.] N. Sikder, Sc 'F'	HEMRL, DRDO, Pune
14.	Shri I.S Kalashetti, Sc 'F'	ARDE / DRDO Orgn, Pune
15.	Shri Rajeev Puri, Addl GM	Ammunition Factory, Pune
16.	Shri V K Chhabra, DADG/Staff Captain (Civ.)	Secretary ASSC

RECORD OF AMENDMENTS

Amendment		Amendment pertains to : Sl. No. / Para No. / Column No.	Authority	Amended by	Signature & Date
No.	Date			Name & Appointment (IN BLOCK LETTERS)	

Sl. No.	CONTENTS	PAGE No.
0.	FOREWORD	1
1.	SCOPE	3
2.	RELATED SPECIFICATIONS / DOCUMENTS	3
3.	MATERIAL	4
4.	MANUFACTURE	4
5.	TENDER SAMPLE	4
6.	PRE - INSPECTION OF STORES / CONSIGNMENT	5
7.	QUALITY ASSURANCE	5
8.	WARRANTY	8
9.	PACKAGING	8
10.	MARKING	8
11.	SAFETY OF OPERATIONS	8
12.	DEFENCE STORES CATALOGUE NUMBER	9
13.	SUGGESTIONS FOR IMPROVEMENT	9
	APPENDICES	10 - 14

0. FOREWORD

0.1 This Joint Services Specification has been prepared by the Armament Standardisation Sub Committee on the authority of the Standardisation Committee, Ministry of Defence.

0.2 This specification has been approved by the Ministry of Defence and is mandatory for use by the Defence Services.

0.3 This document is the revision of JSS 9330 - 03 : 2007 (Revision No.2) and supersedes the same.

0.4 This specification would be used for Manufacture, Supply and Quality Assurance of Polyethylene, Low Density, Linear Low Density, and High Density.

0.5 Quality Assurance Authority for the item covered by this specification is the Controller, Controllerate of Quality Assurance (Military Explosives), Aundh Road, Pune - 411 020. Enquiries regarding technical parameters shall be addressed to the Quality Assurance Authority, while other enquiries shall be referred to :-

The Director,
Directorate of Standardisation,
Ministry of Defence,
'H' Block, Nirman Bhawan PO,
New Delhi - 110 011.

0.6 Non registered users can obtain the following on payment :-

(a) Copies of IS from :-

Bureau of Indian standards,
Manak Bhawan,
9, Bahadur Shah Zafar Marg,
New Delhi - 110 002.
or
Their regional / Branch offices.

(b) Copies of JSS / JSG from :-

The Director,
Directorate of Standardisation
Standardisation Documents Centre,
Ministry of Defence
Room No. 05, 'J' Block,
Nirman Bhawan PO,
New Delhi - 110 011.

0.7 Indian Standard (IS) specifications are available free of cost for registered users on :-

Directorate of Standardisation Website
www.ddpdos.gov.in
For registration visit our website.

0.8 This specification holds good only for the supply order for which it is issued.

0.9 Directorate of Standardisation Website. All the approved JSS / JSGs are available on the Directorate of Standardisation Website **www.ddpdos.gov.in**. Defence Organisations desirous of accessing a copy of this document are requested to approach the Directorate of Standardisation for obtaining user id / password to access the website.

0.10 Copies of ASTM Standards can obtain on payment from :-

American Society for Testing and Materials,
1916 - Race Street,
Philadelphia PA 19103 - 1887 USA

or

Their Official Distributors in India viz :-

Book Supply Bureau,
D - 44, South Extn - 1,
New Delhi - 110 049

1. SCOPE

1.1 This specification is meant to Govern Manufacture, Supply and Quality Assurance of the following grades of polyethylene.

(a) Low density polyethylene type 1 for use in the manufacture of sheets, lay flat tubing, bags used for packing ammunition, ammunition components, ammunition chemical and Explosives and wax special No. 8.

(b) Low density polyethylene type 2 for use in the manufacture of carriers, containers and other moulded components.

(c) Linear low density polyethylene for use in the manufacture of carriers, containers and other moulded components.

(d) High density polyethylene type 1 for use in packing of ammunition components and in the manufacture of washers, sleeves etc used in ammunition.

(e) High density polyethylene type 2 for use in the manufacture of carrier, containers and barmines.

2. RELATED SPECIFICATIONS / DOCUMENTS

2.1 Reference is made in this specification to :-

Sl. No.	Specification No. & Year	Nomenclature
(a)	IS 138 : 1992 (Third Revision) Reaffirmed 2009 AMD 1	Ready Mixed Paint, Marking for Packages and Petrol Containers.
(b)	IS 1060 (Part 1) : 1966 (Revised) Reaffirmed 2009 AMD 5	Methods of Sampling and Test for Paper and Allied Products : Part 1
(c)	IS 1060 (Part 2) : 1960 Reaffirmed 2009	Methods of Sampling and Test for Paper and Allied Products : Part 2
(d)	IS 13360 (Part 5 Sec 1) : 1996 Reaffirmed 2008	Plastics - Methods of Testing Part 5 : Mechanical Properties Sec 1 Determination of Tensile Properties - General Principles.

JSS 9330 - 03 : 2014
(Revision No. 3)

Sl. No.	Specification No. & Year	Nomenclature
(e)	IS 13360 (Part 5 Sec 2) : 1996 Reaffirmed 2008	Plastics - Methods of Testing Part 5 : Mechanical Properties Sec 2 Determination of Tensile Properties - Test Conditions for Moulding and Extrusion Plastics.
(f)	IS 13360 (Part 5 Sec 4) : 1996 Reaffirmed 2008	Plastics - Methods of Testing Part 5 : Mechanical Properties Sec 4 Determination of Izod Impact Strength.
(g)	IS 13360 (Part 5 Sec 5) : 1996 Reaffirmed 2008	Plastics - Methods of Testing Part 5 : Mechanical Properties Sec 5 Determination of Charpy Impact Strength.
(h)	ASTM - D 256	Test Method for Impact Resistance of Plastics and Electrical Insulating Materials.
(j)	ASTM - D 638	Test Method for Tensile Properties of Plastics.
(k)	ASTM - D 648	Test Method for Deflection Temperature of Plastics Under Flexural Load.
(l)	ASTM - D 1238	Test Method for Flow Rates of Thermoplastics by Extrusion Plastometer.

3. **MATERIAL.** Polyethylene Low density, Linear low density and High density shall essentially consist of polymer of Ethylene and shall be free from pigment and plasticizers like Polyisobutylene.

4. **MANUFACTURE.** Polyethylene Low density, Linear low density and High density shall be manufactured by a process which will produce the product conforming to this specification.

5. **TENDER SAMPLE.** The manufacturer / supplier / contractor shall submit a tender sample of 1 kg of moulding powder essentially from the same batch / lot of manufacture alongwith test specimen for the tests mentioned in clause 7.4 free of all charges and conforming to this specification, to the Quality Assurance Authority / Quality Assurance Officer as stated in the contract.

6. PRE - INSPECTION OF STORES / CONSIGNMENT

6.1 Manufacturers / Contractors must satisfy themselves that the stores are in accordance with the terms of the contract and fully conform to the required specification, by carrying out a thorough pre - inspection of each lot before actually tendering the same for inspection to the Quality Assurance Officer nominated under the terms of the contract. A declaration by the contractor that necessary pre - inspection has been carried out on the stores tendered will be submitted alongwith the challan. The declaration will also indicate the method followed in carrying out pre - inspection showing the features checked / tested and will have the test certificate attached to the challan / declaration.

6.2 If the Quality Assurance Officer finds that the pre - inspection of the consignment as required above has not been carried out, the consignment is liable for rejection.

7. QUALITY ASSURANCE

7.1 Inspection.

7.1.1 Polyethylene Low density, Linear low density and High density and the packages in which it is packed shall be subject to inspection by and to the final approval of the Quality Assurance Officer / Quality Assurance Authority.

7.1.2 Samples of the material and of the packages may be taken from any portion of the batch / lot / consignment.

7.2 **Sampling.** The representative sample of 500 g shall be taken from each package selected for sampling from the batch / lot. The number of packages to be selected to draw the samples from the lot are as under:-

Lot Size	No. of Containers to be Selected
Upto 3	Each Container
4 to 15	3
16 to 50	4
51 to 100	5
101 to 300	7
301 to 500	10
501 & above	15

7.3 **Criteria for Conformity.** If on examination, any sample is found not conforming to this specification, the whole batch / lot / consignment may be rejected.

JSS 9330 - 03 : 2014
(Revision No. 3)

7.4 **Test Requirements.** Samples taken from any portion of the batch/lot/consignment of material shall conform to clause 3 and in addition shall conform to the test requirements shown in the following tables :-

(a) **Chemical Requirements.**

Sl. No.	Characteristic	Passing Standard			Test Method
		(Low Density)	(Linear Low Density)	(High Density)	
(a)	Ash, % by mass	Max. 0.05	0.5	0.05	IS 1060 (Part 1) Method 11
(b)	pH of water extract	Min. 5 Max. 8	5 8	5 8	IS 1060 (Part 1) Method 10
(c)	Water soluble matter, % by mass	Max. 0.2	0.2	0.2	Appendix 'A'
(d)	Water soluble chlorides calculated as Sodium Chloride, % by mass	Max. 0.05	0.05	0.05	IS 1060 (Part 2) Method 17
(e)	Water soluble sulphates, calculated as anhydrous Sodium sulphate, % by mass	Max. 0.1	0.1	0.1	IS 1060 (Part 2) Method 18
(f)	Solubility in Toluene at 80 °C ± 1 °C	Soluble	Partially Soluble	Insoluble	Appendix 'B'
(g)	Extractable matter in Toluene at 25 °C ± 1 °C, % by mass	Max. 6.0	6.0	---	Appendix 'C'
(h)	Solubility in Ethyl acetate, Acetone at 25 °C ± 1 °C	Insoluble	Insoluble	Insoluble	Appendix 'D'
(j)	Effect of organic solvents	Resistant below 60 °C	Resistant below 60 °C	Resistant below 80 °C	Appendix 'E'

(b) Physical Requirements.

Sl. No.	Characteristic		Passing Standard					Test Method
			(Low Density		(Linear Low Density)	(High Density)		
			Type			Type		
			1	2		1	2	
(a)	Melt flow index		--	2 ± 20 %	2 ± 20 %	--	8 ± 20 %	ASTM - D 1238
(b)	Density g/ml	Min. Max.	0.910 0.925	0.918 0.922	0.916 0.920	0.941 0.965	0.955 0.959	BS 2782 Pt 6 Method No. 620 A : 1991
(c)	Yield stress, MPa	Min.	7	12	20	21	23	BS 2782 Pt 3 Method 320 A : 1976 (1986)
(d)	Elongation% at yield	Min.	90	560	500	15	10	-- do --
(e)	Impact strength (Notched) in mJ/mm ²	Min.	--	--	--	--	2.7	ASTM - D 256 Method A
*(f)	Melting temperature, °C	Min. Max.	98 115	98 115	122 124	128 133	128 133	--
*(g)	Tensile modulus in MPa	Min.	98	98	350	530	530	ASTM - D - 638
*(h)	Heat deflection temperature at 4.6 kg/cm ² load, °C	Min.	60	60	68	83	83	ASTM - D - 648

Note.

(i) The tests mentioned at Sl. No. (f), (g) & (h) are for information only. The limits for the same will be finalized after generation of date.

(ii) The width of specimen for yield stress and elongation should be 6 mm and rate of traverse of the machine while testing should be 50 mm / minute.

8. WARRANTY. The stores supplied against the contract shall be deemed to be warranted against the defective material and performance by the contractor for a period of 12 months from the date of receipt of the stores at the consignee's end and shall retain the properties described above. If during this period any of the stores supplied is found defective, the same shall be replaced by the manufacturer / supplier / contractor free of charges at the consignee's premises.

9. PACKAGING. The packaging shall be in accordance with the terms of the contract or as agreed to between the purchaser and contractor.

10. MARKING

10.1 All packages containing the material shall be indelibly and legibly marked with the following details:-

- (i) Nomenclature and Specification Number.
- (ii) Name and Address of the Consignee.
- (iii) A/T. or S.O. Number and Date.
- (iv) Consignment Number.
- (v) Lot / Batch Number and Date of Manufacture.
- (vi) Gross and Net Mass.
- (vii) Consecutive Number of Package and Total Number of Packages in the Consignment.
- (viii) Date of Supply.
- (ix) Contractor's Initials or Recognized Trademark.

10.2 In addition to the above the Quality Assurance Officer / Quality Assurance Authority may suggest some more marking / identification considered suitable at the time of inspection.

10.3 The paint used for marking should conform to IS 138.

11. SAFETY OF OPERATIONS. Nothing in this specification shall relieve the manufacture / supplier / contractor of his responsibility for the safety of operations in the manufacture, storage, transit use of this store.

12. DEFENCE STORES CATALOGUE NUMBERS

12.1 Defence Stores Catalogue numbers allotted to the stores are as under :-

Nomenclature	DS Cat. No.
Polyethylene Low Density Type 1	9330 - 000 115
Polyethylene Low Density Type 2	9330 - 000 131
Polyethylene Linear Low Density	9330 - 000 130
Polyethylene High Density Type 1	9330 - 000 117
Polyethylene High Density Type 2	9330 - 000 119

Applicability of the Amendment :-

- (a) Applicable to existing service stores and stores under manufacture.
- (b) Specification can be amended locally.

13. SUGGESTIONS FOR IMPROVEMENT

13.1 Any suggestion for improvement in this document may be forwarded to :-

The Director,
Directorate of Standardisation,
Ministry of Defence,
'H' Block, Nirman Bhawan PO,
New Delhi - 110 011

APPENDIX 'A'

A. PREPARATION OF AQUEOUS EXTRACT AND ESTIMATION OF WATER SOLUBLE MATTER, CHLORIDES AND SULPHATES

A.1 Cover 10 g of sample, cut to small pieces passing through 200 micrometer IS sieve, with 100 ml of boiling distilled water. Allow to stand in a stoppered conical flask for an hour with occasional shaking. Filter through No. 1 Whatman filter paper. Evaporate 25 ml of the above solution in a previously cleaned, dried and weighed glass evaporating dish (M1). On sand bath, keep the dish at 100 °C for 30 minutes. Cool in desiccators and weigh (M2).

$$\text{Water soluble matter \%} = \frac{(M2-M1) \times 100 \times 100}{\text{Mass of the sample taken} \times 25}$$

A.2 Using the remaining extract, estimate chlorides and sulphates as per method 17 and method 18 of IS 1060 (Part 2) respectively.

APPENDIX 'B'

B. SOLUBILITY IN TOLUENE AT 80 °C ± 1 °C

B.1 Samples shall be tested at 80 °C ± 1 °C with Toluene. Three samples of the material 1.5 g each shall be accurately weighed. These are transferred to three Erlenmeyer flasks of 125 ml capacity. To each sample shall then be closed with ground glass stoppers or with rubber stoppers wrapped with Aluminium foil to eliminate any effect of Toluene on the rubber. The mixture shall be stored for 16 hours at 80 °C ± 1 °C. The solubility of polyethylene in Toluene at 80 °C ± 1 °C shall be observed at this temperature. The polyethylene shall be classed as soluble in Toluene at 80 °C if a clear, homogenous solution with no undissolved residue is obtained.

APPENDIX 'C'

C. EXTRACTABLE MATTER IN TOLUENE AT 25 °C ± 1 °C

C.1 Polyethylene - Toluene mixture from Appendix 'B' shall be allowed to cool to 25 °C ± 1 °C. It is advisable not to accelerate the cooling operation. The solution shall be filtered through a sintered glass crucible (G - 3) which has been previously treated in order to remove any Toluene soluble material and to bring it to constant mass by heating at 50 °C ± 1 °C (M2). The solution shall then be transferred to the tared crucible and suction applied to hasten the filtration followed by rinsing of flask with Toluene three times using 15 ml of Toluene each time. After the transfer and rinsing are complete, the final traces of Toluene are completely removed by applying suction.

C.2 The crucible shall then be heated in an oven at 50 °C ± 1 °C to constant mass (M3). During the period when crucible and/or residue is not being heated or weighed, it shall be kept in desiccators with anhydrous Calcium chloride as desiccant.

C.3 The per cent extractable matter in Toluene shall be calculated by the following formula:-

$$\text{Per cent insoluble matter} = \frac{(M3 - M2) \times 100}{M1}$$

Where M1 = The mass of the sample taken for test for Solubility at 80 °C ± 1 °C in Toluene at Appendix 'B'.

C.4 If the value is less than 6.0 %, the material shall be considered insoluble at 25 °C in Toluene and also to have complied with the requirement for extractable matter.

APPENDIX 'D'

D. SOLUBILITY AT 25 °C ± 1 °C IN ETHYL ACETATE, ACETONE

D.1 1.5 g of sample is stored with Acetone and Ethyl acetate separately at 25 °C ± 1 °C for 20 hours with approximately 60 ml of reagent. The solubility shall then be observed by evaporating the solvent or visually.

APPENDIX 'E'

E. EFFECTS OF ORGANIC SOLVENTS

E.1 Immerse a piece of the sample (weighed quantity if in powder form) in an organic solvent (normally Toluene or Ethyl acetate or Amylacetate and in special cases if required Methanol, carbon tetra chloride or dioxine) and maintain at the required temperature (60 °C for grades A & B, low, density and linear low density polyethylene and 80 °C for grade C, High density polyethylene) for 1 hour. Take out the sample and examine it visually. The sample shall not become soft or deformed or no appreciable portion of it shall dissolve in the solvent.

RAKSHA MANTRALAYA/MINISTRY OF DEFENCE
MANKIKARAN NIDESHILAYA/DTE. OF STANDARDISATION

Sheet No. 1
No. of Sheets : 1
Authority :

AMENDMENT LIST No. 1

The following amendment are approved :-

JSS No. & Year	Nomenclature	Details of Amendments	Reason for Amendments
1	2	3	4
JSS 9330-03:2014 (Revision No. 3) DS Cat. No. 9330 - 000 115 9330 - 000 131 9330 - 000 130 9330 - 000 117 9330 - 000 119	Polyethylene Low Density, Linear Low Density and High Density	On page No. 07, Clause 7.4(b) Physical Requirements (a) FOR : Sl. No. (c) Yield Stress MPa READ : Sl. No. (c) Tensile Strength at break in MPa (b) FOR : Sl. No. (d) Elongation % at yield. READ : Sl. No. (d) Elongation % at break.	The amendments are suggested by CQA (ME) Pune, vide their letter No. CQA(ME)/5025/STD/73 Dt. 16 Jun 2015.