


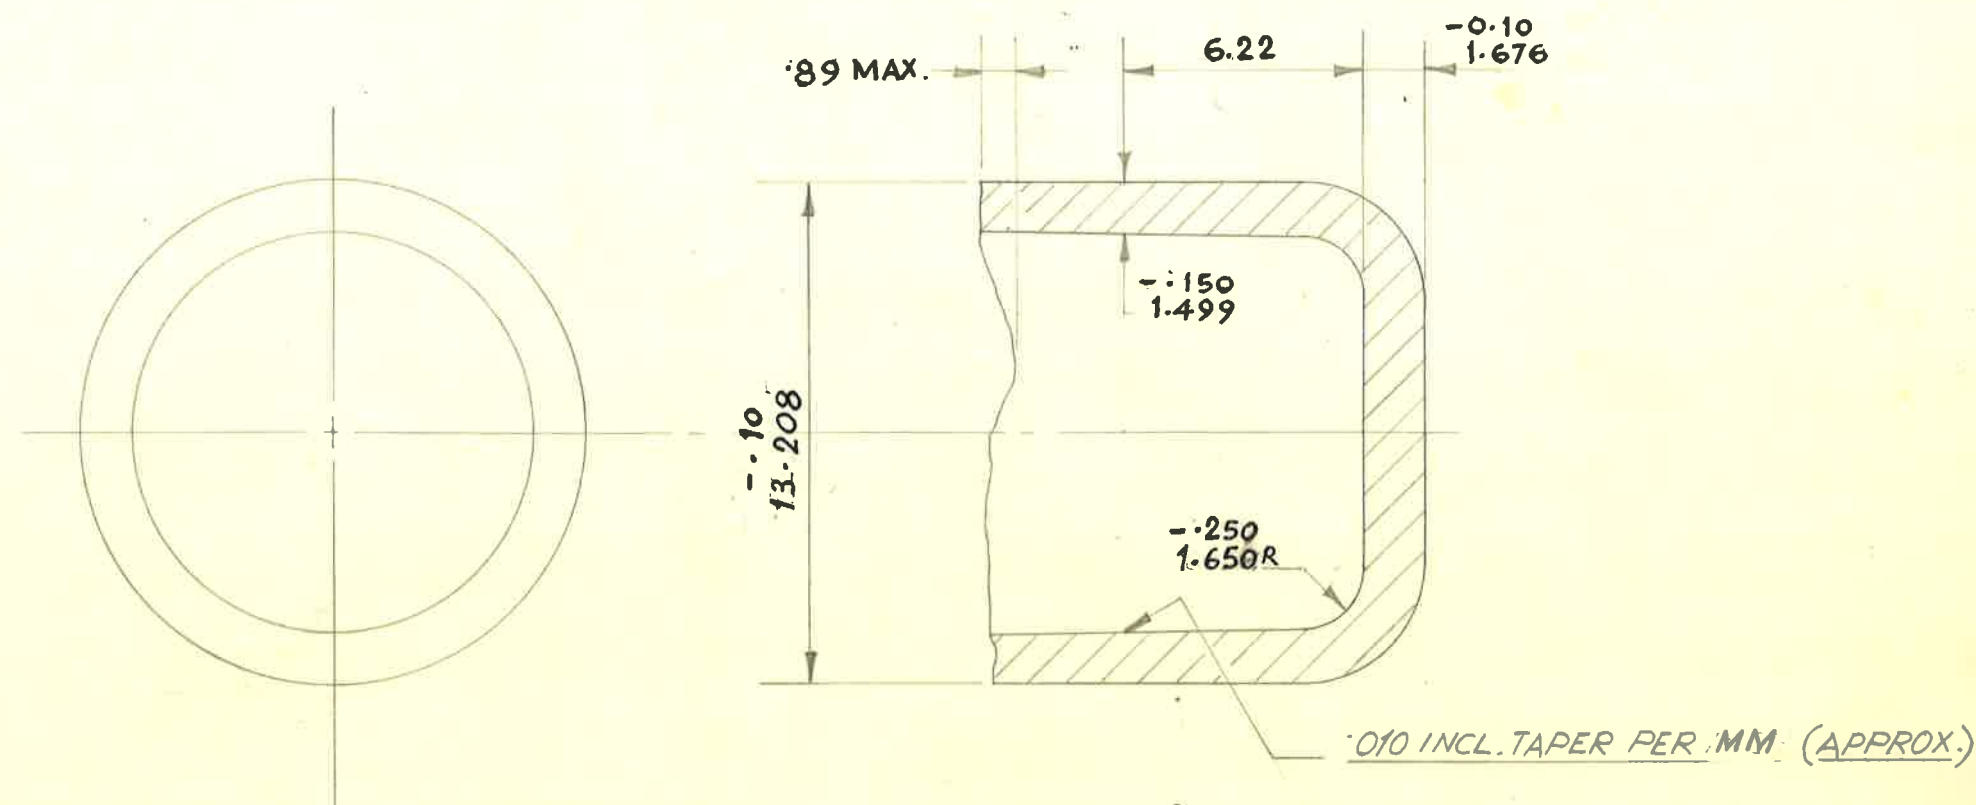

NOTES:-

1. WEIGHT $\pm .32$ 5.314 GRAMMES.
2. STRIP COPPER ALLOY 220 SPCN. NO MIL-C-21768 OR NO. BS/STA/19. IN ANNEALED TEMPER WITH GRAIN SIZE .015MM TO .035MM.
3. CUP SPECN. NO. MIL-C-3383 UNANNEALED HAVING A GRAIN SIZE .04MM MAX. MEASURED ON THE BASE. (TO BE SUPPLIED BY O.F.A./O.F.KATANI.)
4. VARIATION IN WALL THICKNESS OF ANY INDIVIDUAL CUP NOT TO EXCEED 0.076MM.
5. SIDE WALL GRAIN SIZE MAX. .05M.M & MIN. .025M.M. IN ANNEALED CONDITION IN ACCORDANCE WITH THE SPECIFICATION MIL-C-3383. (AFTER ANNEALING AT O.F.V.)
6. V.P.N. ON DOME & WALL 65-75.
7. TOLERANCES UNLESS NOTED ON DECIMALS $\pm .076$ MM.

APPROVED.

FOR GENERAL MANAGER.

DRG. NO. OF V/C/141 AMND. TO READ V/PROD/0018	16.6.67	
DESCRIPTION.	DATE	APPROVAL

1967	DATE	NAME	PROJECTION	ORDNANCE FACTORY,
1/CDQ	5/5	1/2	3RD ANGLE.	VARANGAON.
356	23/78	C'	DRM: 16.6.	CUP G.M. FOR BULLET JACKET 7°62 M.M TRACER M-62.
352	20/78	B'	CHD: 3.7	
356	27/77	A'	SCALE: 581	
NO.	DT.	ALT.	SIG.	
DIMENSIONS ARE IN MM.				SHEETS / SHEET NO. 1
				DRG. NO. V/PROD/0018-C